

## СТРОИТЕЛЬНЫЕ МАТЕРИАЛЫ И ИЗДЕЛИЯ/CONSTRUCTION MATERIALS AND PRODUCTS

DOI: <https://doi.org/10.60797/IRJ.2025.154.58>

## ELECTROPLASMA PROCESSING OF ASH WASTE FROM INCINERATION INTO GLASS-CRYSTAL CAST MATERIALS

Research article

Kondratenko A.S.<sup>1,\*</sup>, Zayakhanov M.E.<sup>2</sup>, Bituev A.V.<sup>3</sup>, Chang F.L.<sup>4</sup><sup>1</sup>ORCID : 0000-0002-2361-5249;<sup>1</sup>Buryat State University, Ulan-Ude, Russian Federation<sup>2,3,4</sup>East Siberian State University of Technology and Management, Ulan-Ude, Russian Federation

\* Corresponding author (cubanit[at]yandex.ru)

**Abstract**

The article examines the characteristics of ash waste obtained at incinerators (China) to establish the possibility of their use as a raw material in the production of glass-crystal casting by electroplasma method. Studies of the granulometric, mineralogical, and chemical composition of the raw materials were performed using dispersion-gravimetric, microscopic, spectral, and X-ray phase analyses. During the study, the true density, specific surface area, granulometric, chemical and mineralogical compositions of the raw materials and the stone castings obtained from it were established with the calculation of the modulus of acidity, which amounted to  $M_k = 2,73$ , which makes it possible to produce casting from a single-component charge (ash waste). In the process of electroplasmic melting of raw materials, a calcium-silicate stone casting was obtained, which is a crystallized melt of a given geometric shape made of quartz ( $\text{SiO}_2$ ) in its glass phase. The data obtained in the course of the conducted studies allow us to recommend electroplasma melting as a method of processing ash waste from incineration into a melt with low energy consumption (0,8–1,0 kWh/kg), and classify the produced product as a calcium-silicate glass-crystal casting.

**Keywords:** ash waste from incineration, density, granulometry, specific surface area, chemical, mineralogical composition, modulus of acidity, electroplasmic melting, glass-crystal casting.

## ЭЛЕКТРОПЛАЗМЕННАЯ ПЕРЕРАБОТКА ЗОЛОТХОДОВ ОТ СЖИГАНИЯ В СТЕКЛОКРИСТАЛЛИЧЕСКИЕ ЛИТЫЕ МАТЕРИАЛЫ

Научная статья

Кондратенко А.С.<sup>1,\*</sup>, Заяханов М.Е.<sup>2</sup>, Битуев А.В.<sup>3</sup>, Чан Ф.Л.<sup>4</sup><sup>1</sup>ORCID : 0000-0002-2361-5249;<sup>1</sup>Бурятский государственный университет, Улан-Удэ, Российская Федерация<sup>2,3,4</sup>Восточно-Сибирский государственный университет технологий и управления, Улан-Удэ, Российская Федерация

\* Корреспондирующий автор (cubanit[at]yandex.ru)

**Аннотация**

В статье рассмотрены характеристики золоотходов, полученных в мусоросжигательных печах (Китай), с целью установления возможности их использования в качестве сырья для производства стеклокристаллического литья электроплазменным методом. Изучение гранулометрического, минералогического и химического состава сырья проводилось с помощью дисперсионно-гравиметрического, микроскопического, спектрального и рентгенофазового анализов. В ходе исследования установлены истинная плотность, удельная поверхность, гранулометрический, химический и минералогический составы сырья и получаемых из него каменных отливок с расчетом модуля кислотности, который составил  $M_k = 2,73$ , что позволяет производить отливки из однокомпонентной шихты (золоотходов). В процессе электроплазменной плавки сырья была получена кальций-силикатная каменная отливка, представляющая собой закристаллизованный сплав заданной геометрической формы из кварца ( $\text{SiO}_2$ ) в стеклофазе. Полученные в ходе проведенных исследований данные позволяют рекомендовать электроплазменное плавление как способ переработки золоотходов от сжигания в расплав с низкими энергозатратами (0,8–1,0 кВт·ч/кг), а полученный продукт классифицировать как кальций-силикатное стеклокристаллическое литье.

**Ключевые слова:** золоотходы от сжигания, плотность, гранулометрия, удельная поверхность, химический, минералогический состав, модуль кислотности, электроплазменное плавление, стеклокристаллическое литье.

**Introduction**

In recent years, special attention has been paid to the efficient use of man-made, recycled and recycled waste in the production of various building materials and products [1]. The resource consumption of modern society generates a large amount of substandard waste stored and accumulated in landfills and landfills, which worsen the environmental situation near their locations [2]. One of the most reliable and economically feasible ways to eliminate waste worldwide is its sorting and incineration at incinerators and plants called recycling [3]. But when burning any type of garbage (municipal, industrial, etc.), a solid, non-flammable residue inevitably forms. Therefore, industrial incineration processing leads to the accumulation of huge amounts of ash waste from incineration in the form of powdered dust [4]. In addition to being highly dispersed and prone to dusting, the waste presented is low-resistant, leachable in aggressive agents (mineral and organic acids), highly hygroscopic, susceptible to chemical weathering, and therefore substances of very limited use. But despite this, ash waste from incineration is a valuable secondary resource because ash dumps in landfills, with thoughtful and rational processing, can serve as sources

of raw materials for other industries [5]. To achieve maximum efficiency (minimizing costs and environmental risk), it is necessary to implement integrated technological solutions in which the use of some waste leads to the neutralization and effective processing of others [6].

One of the ways to process ash from incineration may be to melt them in order to obtain a melt with further production of stone-like cast materials based on it. Preliminary experiments on electropasmic melting of ash waste have shown the fundamental possibility of obtaining a melt and producing stone casting from it [7]. The study of the obtained products showed that its composition is represented by a quartz-containing  $\text{SiO}_2$  phase with a concentration of 25,32%. The X-ray image also shows a solid halo of a glass phase containing this phase. Therefore, during further research, **the following tasks were set:** to calculate the actual density, specific surface area, granulometric, chemical and mineralogical compositions of raw materials to determine the content of calcium and silicon oxides, which determine the formation of the required structure during melting and shaping; to calculate the modulus of acidity of the melt to solve the problem of priming during melting; to clean the exhaust gases, formed during the melting of ash waste containing volatile compounds; in an electroplasma installation designed according to the type of electromagnetic reactor, a melt is obtained from which, by pouring into side molds, a stone-like casting of specified geometric shapes is developed.

The search for new raw materials, as well as ways of processing them to obtain glass-crystalline materials and products, is an urgent task for the needs of the construction industry [8]. In addition, significant characteristics of the physical and technological properties of these materials such as high abrasive, chemical and thermal resistance, long service life have predetermined their use as cladding and cast products resistant to abrasive wear. Thus, glass-crystal casting tiles are used as lining linings for flues, bunkers, cleaners, as well as floors and gutters of various equipment that can withstand a large number of freeze-thaw cycles [9]. However, a limiting factor in the synthesis of these materials is high gas formation and the presence of potentially harmful substances in the ash, which complicates the production processes [10]. Based on these facts, **the purpose of this study was formed** — to study the most important characteristics of substandard raw materials in the form of ash waste from incineration and to establish the possibility of its use in the production of cast glass crystal products (stony materials) by melting in an atmospheric environment using the energy of arc electropasm with associated purification of the resulting flue gases. In comparison with the currently existing methods of synthesizing the presented materials, this method is easier to implement, and therefore preferable from the point of view of the possibility of organizing further production [11], [12].

#### Materials and methods of research

The object of the research was fine-grained ash formed as a residue during the incineration of municipal waste at incinerators in China. The following scientific equipment was used in the work, provided by the PROGRESS Central Research Institute of ESSUTM, as well as the BSC SB RAS: Le Chatelier flask (Russia); electronic scales Sigma-scale 100/0,001 (USA); device for determining the specific surface area of powders PSX-2 (Russia); mechanical dispersion device (sieve analyzer) A-20 (Russia); digital polarizing microscope Altami POLAR 1 (Russia); X-ray diffractometer D8 Advance AXS BRUKER (Germany); atomic absorption spectrometer Solaar M6 Thermo Electron (USA); synchronous thermal analysis device STA 449 F1 Jupiter (Germany); capillary electrophoresis unit Drops-105 (Russia). The chemical and mineralogical compositions of raw materials and products were studied using microscopic, spectral and X-ray phase analyses. The fractional composition was studied using a sieve and gravimetric method, and the specific surface area was calculated using a PSX-2 device.

Optical microscopy in transmitted polarized light was used to determine the morphological characteristics of the raw material and the particle size, which determines the structure and dispersion of the material (Fig. 1).

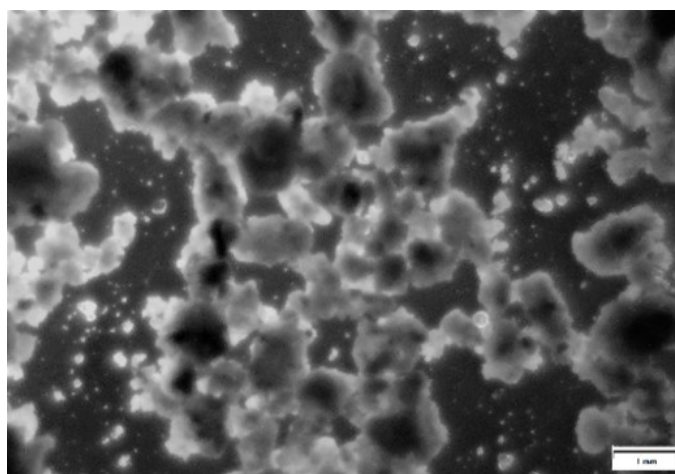


Figure 1 - Powdered ash of incineration  
DOI: <https://doi.org/10.60797/IRJ.2025.154.58.1>

Note: 40x

By the method of microanalysis of raw materials, it was found that ash waste from incineration is a powdery substance consisting of small, flake-like particles and their agglomerates, as well as individual large grains.

Further studies were carried out to establish the true density, fractional composition and specific surface area of the raw material [13]. The density was calculated by the volume-weight method using a Le-Chatelier flask using formula 1:

$$\rho = \frac{m}{v}, \text{ kg/m}^3, \quad (1)$$

where  $m$  — is the mass of waste consumed in the experiment;  $v$  — is the volume of liquid after pouring the raw materials. The specific surface area of powdered ash was determined on a PSX-2 device using the formula 2:

$$S_{s.s.} = \frac{KM\sqrt{\tau}}{m}, \text{ cm}^2/\text{g}, \quad (2)$$

where  $K$  — is the constant of the device for a pair of plates between which a column of liquid was observed to fall during a time of  $\tau$ , sec.;  $M$  — is the value determined from the measured values of the layer height  $H$  and air temperature (the values of  $K$  and  $M$  are contained in the device passport);  $m$  — is the weight of the suspension, g.

The grain composition was determined using a mechanical dispersion device (A-20 sieve analyzer) with a standard set of sieves. The data on the ash waste study are presented in Table 1.

Table 1 - Granulometric composition and specific surface area of ash waste

DOI: <https://doi.org/10.60797/IRJ.2025.154.58.2>

Fraction, mm	0,3	0,2	0,1	0,05	<0,05
Content, %	6,24	18,20	55,60	18,24	1,72
Specific surface area, $\text{cm}^2/\text{g}$	645	1027	1572	2064	3704

The calculated true density of ash waste was  $\rho = 2707 \text{ kg/m}^3$ , and the fractional composition and specific surface area indicated qualitative changes and transformations that occurred with the original substance (sorting, crushing and separation followed by thermochemical action).

The possibilities of processing any materials directly depend on knowledge of their chemical composition, which determines the methods of exposure to them. Therefore, further studies conducted by methods of physico-chemical analysis were aimed at establishing the chemical composition and determining the main components of ash waste from incineration.

To study the chemical and mineralogical composition of raw materials according to GOST ISO 5725-6-2003, an analytical sample of 0,1 mm fraction was obtained by averaging and quartering (it is the dominant and therefore the host fraction). The chemical analysis of the ash was carried out using titrimetric, gravimetric, and photometric methods, as well as a Solaar M6 Thermo Electron atomic absorption spectrometer. The chemical composition of the ash waste is presented in Table 2.

Table 2 - Chemical composition of ash waste from incineration

DOI: <https://doi.org/10.60797/IRJ.2025.154.58.3>

Substance	SiO <sub>2</sub>	Al <sub>2</sub> O <sub>3</sub>	FeO+Fe <sub>2</sub> O <sub>3</sub>	MgO	CaO	Na <sub>2</sub> O	K <sub>2</sub> O	TiO <sub>2</sub>	P <sub>2</sub> O <sub>5</sub>	SO <sub>3</sub>	CuO	ZnO	C	Cl
Mass fraction, %	12,84	4,82	2,63	2,78	26,43	3,10	2,85	0,51	2,60	5,28	0,74	1,29	24,43	9,70

The chemical composition of the studied raw materials allowed us to establish a high concentration of carbon, calcium, silicon, potassium and sodium contained in it, as well as phosphorus and chlorine, which form the basis of most organic and inorganic substances and compounds that form waste. Thus, it was shown that ash waste consists of almost 25% of the carbon component of the "organic part", while the remaining 75% is represented by a complex composition of elements forming an "inorganic complex" or mineral mass. Qualitatively and quantitatively, the ash composition is most likely formed not only from the elements included in the waste, but also introduced, passing into the substance from burning and supporting gorenje energy carriers (coal, fuel oil, etc.) [14], [15].

To identify the crystallographic phases that make up the incineration ash, its X-ray phase analysis (XFA) was performed [16]. X-ray diffraction was performed on a BRUKER AXS D8 Advance X-ray diffractometer in Cu K $\alpha$  radiation. X-ray images were taken in the range of angles of 2  $\theta$  from 0° to 70° in increments of 0,03°, with a scanning speed of 2.0 degrees/min. The data bank of PDF-2 powder radiographs of organic, inorganic, mineral and synthetic compounds was used for the analysis. The quantitative phase ratio was determined in the TOPAS 4.2 program by the Rietveld method.

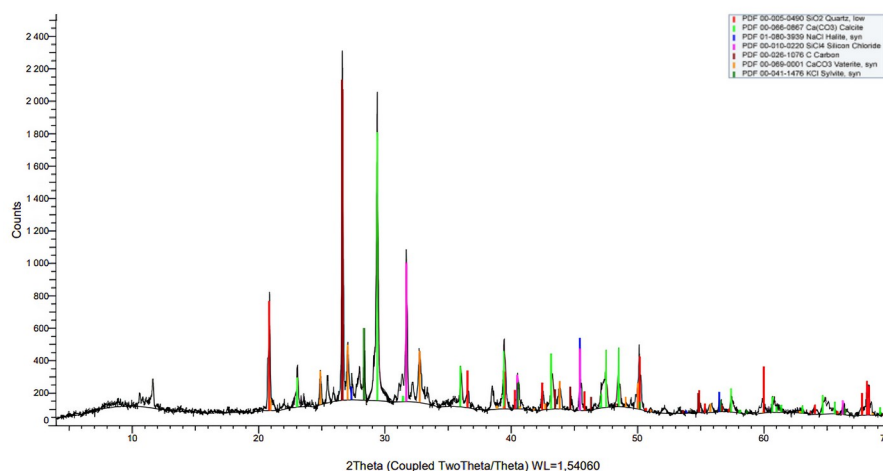


Figure 2 - X-ray phase diagram of ash waste from incineration  
DOI: <https://doi.org/10.60797/IRJ.2025.154.58.4>

*Note: the phases of quartz, calcite, halite, sylvinite, and carbon are presented*

According to the X-ray phase analysis of the mineralogical composition (Fig. 2), ash waste is composed of crystallographic phases of silicates (quartz), carbonates (calcite), chlorides (sodium, potassium, etc.), as well as phases of crystalline and amorphous carbon.

The presence of elements such as carbon, chlorine, sulfur and phosphorus in the composition of ash potentially complicates the process of its processing. Therefore, additional research was required to establish the thermal stability of the raw materials [17]. The tests were carried out on a synchronous thermal analysis device STA 449 F1 Jupiter.

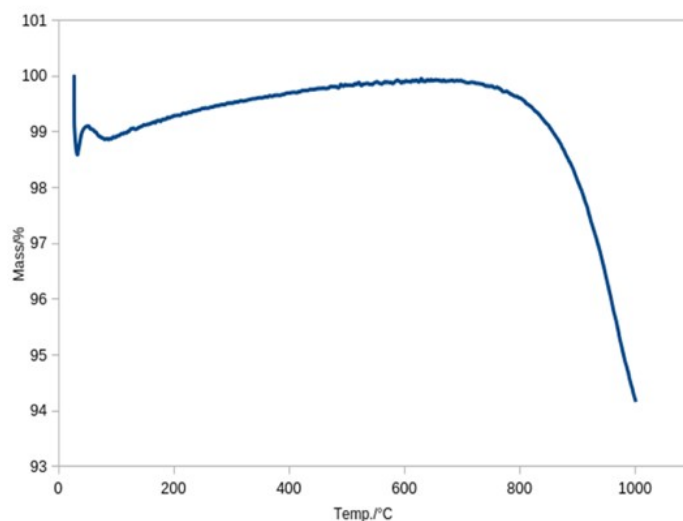


Figure 3 - TGA diagram of phase transformations of ash waste  
DOI: <https://doi.org/10.60797/IRJ.2025.154.58.5>

Phase transformations and chemical reactions occurring in the substance during its heating were studied using thermogravimetric analysis (Fig. 3). Analysis of the TGA curve allowed us to conclude that the ash waste under study behaves the same way as classical silicate group materials [18]. The thermogram at the initial stage of heating in the temperature range of 50–100°C was characterized by the endothermic effect of evaporation of free moisture, then a monotonously increasing exothermic effect in the temperature range of 200–750°C indicated phase and chemical transformations associated with both the burning of carbon (organic residues) and the removal of absorbent and chemically bound moisture, and the formation of crystallization centers with the transformation of an amorphous phase crystallization and recrystallization of calcium and magnesium silicates of complex composition. A sharp endothermic effect in the higher temperature range (800–1000°C) indicated the evaporation of low-melting compounds (chlorides, sulfates, phosphates) present in the ash.

#### The results of the study and their discussion

As a result of the study of the composition and structure of the raw material, reliable data were obtained on its melting to obtain a silicate melt and the production of glass-crystal casting from it [19], [20]. For this purpose, a series of experiments was conducted, with the development of smelting modes using electroplasma melting equipment designed in the form of an electromagnetic process reactor. Thermal energy in the electric arc zone of the reactor chamber was generated by plasma-ohmic heating. Thus, this zone was both a zone of heat energy generation and a zone of its absorption, making it possible to regulate (by increasing or decreasing the current strength) the melting time of raw materials in it [21], [22], [23]. Structurally, the operating principle of the reactor is presented as follows: an electric arc burns in the reactor chamber between the three-phase electrodes, and electromagnetic windings serially connected to the electrodes create a rotating magnetic field that simultaneously mixes the melt, thereby contributing to its homogenization and eliminating non-melting zones. The schematic diagram of the plant for electroplasma melting of raw materials is shown in Figure 4.

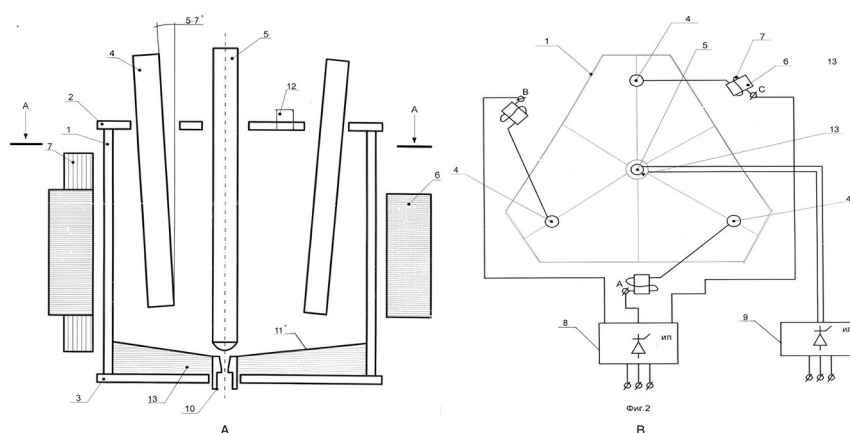


Figure 4 - Longitudinal (A) and transverse (B) sections of an electromagnetic process reactor  
DOI: <https://doi.org/10.60797/IRJ.2025.154.58.6>

Note: 1 – reaction chamber; 2 – water-cooled lid; 3 – water-cooled bottom; 4 – rod electrodes (3 pcs.); 5 – rod locking

electrode; 6 – pole tip; 7 – series winding; 8 – power source; 9 – additional power source for heating the jet; 10 – device for removing the melt (letka); 11 – lined bottom of the chamber; 12 – pipe into the reaction chamber for feeding raw materials; 13 – lining

A series of experiments conducted on melting the ash residue of incineration showed high gas formation during the melting of this waste. Therefore, it was decided to produce dry gas purification by gas absorption with a sorbent (activated carbon + mineral fiber carrier). Initially, the gas cleaning device was a filter installed in the exhaust. The purpose of the tasks set in this case was both to obtain a homogeneous melt with the subsequent production of casting from it, and the associated purification of the resulting flue gases. During the experiment, the melting of ash weighing 40 kg took place calmly without boiling with high gas emission, the estimated melting time was 35–40 minutes at a reactor power of 15 kW. The technological process of melting the melt and its transformation into casting, as well as the view of the forming chamber are shown in Figures 5, 6.

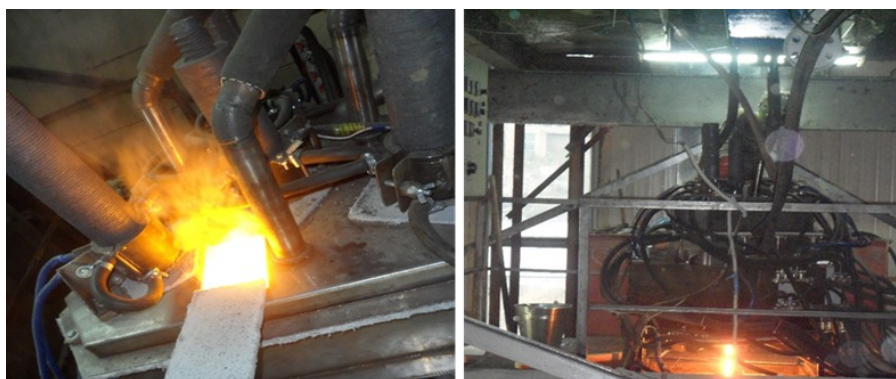


Figure 5 - Electroplasmic melting of raw materials, as well as the moment of fusion of the melt with the production of stone casting

DOI: <https://doi.org/10.60797/IRJ.2025.154.58.7>



Figure 6 - Discharge of the melt jet from the reactor vessel and its casting into molds

DOI: <https://doi.org/10.60797/IRJ.2025.154.58.8>

When the melting process was completed and the melt was formed, the central locking electrode was lifted, and the melt flowed out of the bowl. Then, when it was poured into the flasks (mold), the casting of a given shape was formed (Fig. 7).





Figure 7 - Examples of cast materials (tiles and cylinders in section) obtained from the melt  
DOI: <https://doi.org/10.60797/IRJ.2025.154.58.9>

However, during the further operation of the solid-state filter, difficulties arose due to the rapid deactivation of the sorbent, clogging and subsequent failure of the gas purification module of the melting plant. Therefore, the sorption module was replaced with a single-stage bubbling cleaning system (Fig. 8).



Figure 8 - Water-bubbling gas purification system, formed during the melting of ash waste from incineration  
DOI: <https://doi.org/10.60797/IRJ.2025.154.58.10>

The high gas formation that occurs during the melting of raw materials required additional investigation of demineralized water used to absorb exhaust gases in order to study their composition. The study was carried out by capillary electrophoresis at the "Drops-105" facility. Data on the composition of substances forming exhaust gases absorbed by the water treatment system are presented in Table 3.

Table 3 - Cationic and anionic composition of scavenger water

DOI: <https://doi.org/10.60797/IRJ.2025.154.58.11>

№	Cations	Conc., mg/l	Anions	Conc., mg/l
1	NH <sub>4</sub>	5,45	Chloride ions	401
2	K	248	Nitrite ions	6,91
3	Na	490	Sulfate ions	90,8
4	Li	0,210	Nitrate ions	2,84
5	Mg	51,9	Fluoride ions	8,93
6	Ca	79,6	Phosphate ions	10,9
7	—	—	Bromide ions	9,08
8	—	—	Iodide ions	3,76

Further studies of the resulting casting were aimed at determining its phase-mineralogical composition based on X-ray phase analysis data, as well as studying the main components of the chemical composition by methods of physico-chemical analysis with the calculation of the modulus of acidity.

The study of the casting structure to determine its phase-mineralogical composition was carried out by X-ray phase analysis, shown in Figure 9.



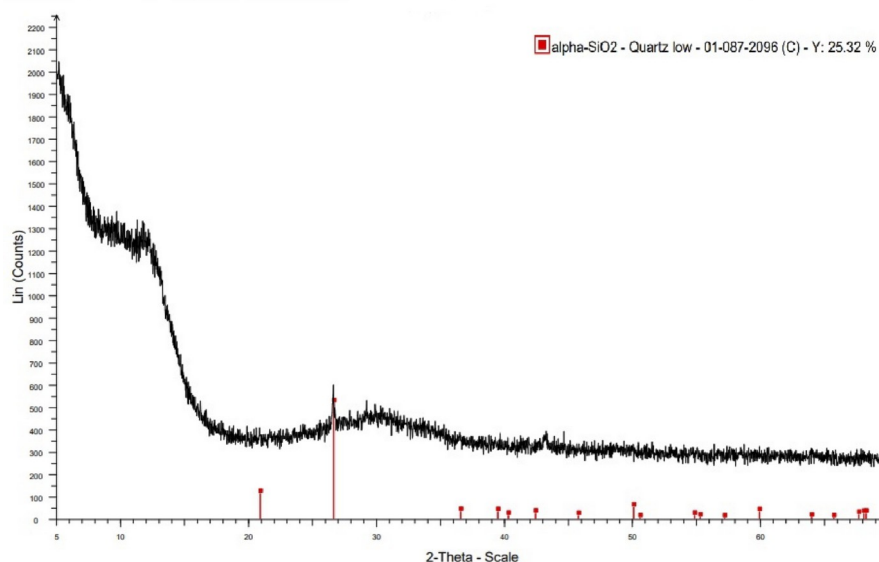


Figure 9 - X-ray diffraction pattern of glass crystal casting obtained by electroplasma method

DOI: <https://doi.org/10.60797/IRJ.2025.154.58.12>

According to the X-ray phase analysis of the mineralogical composition, the casting contains a single crystalline phase with diffraction maxima of quartz ( $\text{SiO}_2$ ). The amount of this phase is at least 25.32%. The X-ray image also shows a solid halo of a glass phase containing this crystalline phase.

The final stage of the research was the determination of the main components of the chemical composition of the casting produced from the melt by methods of physico-chemical analysis with the calculation of its modulus of acidity. The quantitative data of the casting obtained using thermal plasma are presented in Table 4.

Table 4 - Chemical composition of glass crystal casting obtained from waste incineration ash

DOI: <https://doi.org/10.60797/IRJ.2025.154.58.13>

Substance	$\text{SiO}_2$	$\text{Al}_2\text{O}_3$	$\text{FeO} + \text{Fe}_2\text{O}_3$	$\text{MgO}$	$\text{CaO}$	$\text{Na}_2\text{O}$	$\text{K}_2\text{O}$	$\text{TiO}_2$	$\text{P}_2\text{O}_5$
Mass fraction, %	53,41	14,76	1,84	6,64	18,32	2,49	0,45	0,62	1,47

Then, after determining the chemical composition, the acidity modulus was calculated, characterizing the acid-base properties [24]. This module is used for a preliminary assessment in order to determine the suitability for producing a melt and casting from it and is determined by the formula 3:

$$M_k = \frac{(\text{SiO}_2 + \text{Al}_2\text{O}_3)}{\text{CaO} + \text{MgO}}, \quad (3)$$

where  $\text{SiO}_2$ ,  $\text{Al}_2\text{O}_3$ ,  $\text{CaO}$ ,  $\text{MgO}$  are the content of basic oxides, mass %.

To obtain a melt that contributes to the production of high-quality casting, the modulus of acidity of the rock must be in the range of values from two to six [25]. In this case,  $M_k = 2.73$ , which makes it possible to obtain glass crystal casting in the process of electroplasma melting from single-component raw materials without mixing.

The data obtained in the course of the conducted studies allow us to recommend electroplasma melting as a method of processing ash waste from incineration into a melt with low energy consumption (0,8-1,0 kWh/kg), and classify the produced product as a calcium-silicate glass-crystal casting [26].

### Conclusion

In the course of the study, the following results were obtained:

1. The actual density, specific surface area, granulometric, chemical and mineralogical (X-ray phase analysis) compositions of raw materials consisting of ash waste from incineration have been calculated. An increased content of calcium and silicon oxides has been established, which determine both the formation of the glass crystal structure of the casting and the stability of the melting and shaping process. The high content of calcium oxides also indicated that the composition of the resulting casting would be calcium silicate.

2. The modulus of the melt acidity was calculated, which amounted to  $M_k = 2.73$ , which made it possible to obtain stone casting in the process of electroplasma melting from single-component raw materials without its mixing.

3. With the help of a simple water-bubbling system, the exhaust gases generated during the melting of ash waste were cleaned.

4. In an electroplasma installation designed according to the type of electromagnetic reactor, a melt was obtained, from which a glass crystal casting of specified geometric shapes was developed by pouring into side molds.

Thus, the conducted complex of studies allows us to recommend electroplasma melting as a method of processing ash waste from incineration into a melt with low energy consumption (0,8-1,0 kWh/kg), and classify the produced product as a calcium-silicate glass-crystal casting.

### Финансирование

Работа проводилась в рамках государственной субсидии правительства Республики Бурятия Бурятскому государственному университету имени Доржи Банзарова, проект № 696 от 22.11.2024.

### Благодарности

The work was carried out within the framework of a state subsidy from the government of the Republic of Buryatia to the Buryat State University named after Dorji Banzarov, project No. 696 11.22.2024.

### Конфликт интересов

Не указан.

### Рецензия

Все статьи проходят рецензирование. Но рецензент или автор статьи предпочли не публиковать рецензию к этой статье в открытом доступе. Рецензия может быть предоставлена компетентным органам по запросу.

### Funding

The work was carried out within the framework of a state subsidy from the government of the Republic of Buryatia to the Buryat State University named after Dorji Banzarov, project No. 696 11.22.2024.

### Acknowledgement

The work was carried out within the framework of a state subsidy from the government of the Republic of Buryatia to the Buryat State University named after Dorji Banzarov, project No. 696 11.22.2024.

### Conflict of Interest

None declared.

### Review

All articles are peer-reviewed. But the reviewer or the author of the article chose not to publish a review of this article in the public domain. The review can be provided to the competent authorities upon request.

### Список литературы / References

1. Дрейер А.А. Твердые промышленные и бытовые отходы, их свойства и переработка / А.А. Дрейер, А.Н. Сачков, К.С. Никольский [и др.]. — Москва : Просвещение, 2004. — 62 с.
2. Аганов А.А. Обращение с твердыми коммунальными и промышленными отходами. Вопросы моделирования и прогнозирования / А.А. Аганов, С.Ю. Глухов, В.В. Журкович [и др.]. — 4-е изд. — Санкт-Петербург : Лань, 2023. — 352 с.
3. Демьянова В.С. Преимущества раздельного сбора и сортировки твердых бытовых отходов / В.С. Демьянова, О.В. Егоров // Экология урбанизированных территорий. — 2010. — № 3. — С. 76–79. — EDN MXGQOX.
4. Ершов А.Г. Термическое обезвреживание отходов: теория и практика, мифы и легенды / А.Г. Ершов, В.Л. Шубников // Твердые бытовые отходы. — 2014. — № 5 (95). — С. 46–52. — EDN SCPFUT.
5. Соломин И.А. Выбор оптимальной технологии переработки ТБО / И.А. Соломин, В.Н. Башкин // Экология и промышленность России. — 2005. — № 9. — С. 42–45. — EDN JXUKFH.
6. Фоменко А.И. Зола мусоросжигательных заводов как техногенный сырьевой ресурс для извлечения редкоземельных элементов / А.И. Фоменко, Л.И. Соколов // Экология и промышленность России. — 2017. — Т. 21. — № 12. — С. 28–31. — DOI: 10.18412/1816-0395-2017-12-28-31. — EDN ZUMFBB.
7. Buyantuev S.L. Waste Industrial Processing of Boron-Treated by Plasma Arc to Produce the Melt and Fiber Materials / S.L. Buyantuev, N. Guiling, E.T. Bazarsadaev [et al.] // Lecture Notes in Electrical Engineering. — 2016. — Vol. 365. — Chapter 38. — P. 353–361. — DOI: 10.1007/978-981-287-988-2\_38. — EDN WRWCHT.
8. Дворкин Л.И. Строительные материалы из отходов промышленности / Л.И. Дворкин, О.Л. Дворкин. — Москва : Феникс, 2007. — 368 с.
9. Буянтуев С.Л. К вопросу получения каменного литья из базальта местного месторождения электродуговым способом / С.Л. Буянтуев, А.С. Кондратенко, В.Т. Буянтуев [и др.] // Вестник Восточно-Сибирского государственного университета технологий и управления. — 2023. — № 4 (91). — С. 87–95. — DOI: 10.53980/24131997\_2023\_4\_87. — EDN FPMLIS.
10. Weibel G. Chemical associations and mobilization of heavy metals in fly ash from municipal solid waste incineration / G. Weibel, U. Eggenberger, S. Schlumberger [et al.] // Waste Management. — 2017. — Vol. 62. — P. 147–159. — DOI: 10.1016/j.wasman.2016.12.004.
11. Buyantuev S.L. Recycling of the Ash Waste by Electric Plasma Treatment to Produce Fibrous Materials / S.L. Buyantuev, E.T. Bazarsadaev, A.B. Khmelev // Lecture Notes in Electrical Engineering. — 2016. — Vol. 365. — Chapter 34. — P. 319–326. — DOI: 10.1007/978-981-287-988-2\_34. — EDN WRWEPJ.
12. Никифоров А.А. Исследование плазменной технологии получения силикатных тугоплавких расплавов / А.А. Никифоров, Е.А. Маслов, Н.К. Скрипникова [и др.] // Теплофизика и аэромеханика. — 2009. — Т. 16. — № 1. — С. 159–163. — EDN KJUKZF.
13. Гавриленко В.В. Современные методы исследования минералов, горных пород и руд / В.В. Гавриленко. — Санкт-Петербург : Санкт-Петербургский государственный горный институт имени Г.В. Плеханова, 1997. — 137 с.
14. Парецкий В.М. Полезное использование шлаков мусоросжигания / В.М. Парецкий, А.А. Комков, А.Ю. Мамаев // Твердые бытовые отходы. — 2011. — № 4 (58). — С. 51–56. — EDN NEAINB.

15. Саркисов П.Д. Извлечение стекла из твердых городских отходов / П.Д. Саркисов, Р.М. Чернякова, П.Д. Петров // Стекольная промышленность. — 1986. — Вып. 8. — С. 13–15.
16. Гонопольский А.М. Некоторые физико-химические свойства золошлаковых отходов мусоросжигательных заводов / А.М. Гонопольский, М.М. Дыган, А.А. Тимофеева // Экология и промышленность России. — 2008. — № 7. — С. 36–39. — EDN JVRXBN.
17. Ситникова В.Е. Методы термического анализа. Практикум / В.Е. Ситникова, А.А. Пономарева, М.В. Успенская. — Санкт-Петербург : Университет ИТМО, 2021. — 152 с. — EDN SXYAMM.
18. Власов В.А. Плазменные технологии создания и обработки строительных материалов / В.А. Власов, Г.Г. Волокитин, Н.К. Скрипникова [и др.]. — Томск : Издательство Научно-технической литературы, 2018. — 512 с.
19. Буянтуйев С.Л. Переработка золошлаковых отходов электродуговой плазмой для получения композиционных строительных материалов / С.Л. Буянтуйев, Л.А. Урханова, А.Б. Хмелев [и др.] // Вестник ВСГУТУ. — 2016. — № 4 (61). — С. 19–26. — EDN WJSWUN.
20. Саркисов П.Д. Направленная кристаллизация стекла – основа получения многофункциональных стеклокристаллических материалов / П.Д. Саркисов. — Москва : Российский химико-технологический университет им. Д.И. Менделеева, 1997. — 218 с. — EDN ZOPWAN.
21. Худякова Л.И. Местное сырье для производства минерального волокна / Л.И. Худякова, С.Л. Буянтуйев, В.Т. Буянтуйев // Строительные материалы. — 2022. — № 12. — С. 6–9. — DOI: 10.31659/0585-430X-2022-809-12-6-9. — EDN KXCFVP.
22. Шеховцов В.В. Получение стеклокерамики системы MgO–SiO<sub>2</sub> методом плазменной плавки / В.В. Шеховцов, О.Г. Волокитин, В.А. Ушков [и др.] // Письма в ЖТФ. — 2022. — Т. 48. — Вып. 24. — С. 15–18. — DOI: 10.21883/PJTF.2022.24.54017.19278. — EDN WAAUDL.
23. Волокитин О.Г. Особенности физико-химических процессов получения высокотемпературных силикатных расплавов / О.Г. Волокитин, В.И. Верещагин // Известия высших учебных заведений. Серия: Химия и химическая технология. — 2013. — Т. 56. — № 8. — С. 71–76. — EDN QZESVF.
24. Павлушкин Н.М. Химическая технология стекла и ситаллов / Н.М. Павлушкин. — Москва : Стройиздат, 1983. — 432 с.
25. Хан Б.Х. Оценка технологических характеристик петругических расплавов при использовании пироксенового модуля / Б.Х. Хан, М.Б. Строщенко // Проблемы каменного литья. — Киев : Наукова Думка, 1975. — Вып. 3. — С. 184–192.
26. Лясин В.Ф. Облицовочные стеклянные и стеклокристаллические материалы / В.Ф. Лясин, П.Д. Саркисов. — Москва : Высшая школа, 1988. — 146 с. — EDN ZOPEYH.

### Список литературы на английском языке / References in English

1. Dreyer A.A. Tverdye promyshlennye i bytovye othody, ih svoystva i pererabotka [Solid industrial and household waste, their properties and processing] / A.A. Dreyer, A.N. Sachkov, K.S. Nikolsky [et al.]. — Moscow : Prosveshchenie, 2004. — 62 p. [in Russian]
2. Aganov A.A. Obrashchenie s tverdymi kommunal'nymi i promyshlennymi othodami. Voprosy modelirovaniya i prognozirovaniya [Solid municipal and industrial waste management. Issues of modeling and forecasting] / A.A. Aganov, S.Ju. Glukhov, V.V. Zhurkovich [et al.]. — 4th edition. — Saint Petersburg : Lan', 2023. — 352 p. [in Russian]
3. Demyanova V.S. Preimushhestva razdel'nogo sbora i sortirovki tverdyh bytovykh othodov [Advantages of the separate collection and grading of the solid domestic garbage] / V.S. Demyanova, O.V. Egorov // Jekologija urbanizirovannykh territorij [Ecology of urbanized territories]. — 2010. — № 3. — P. 76–79. — EDN MXGQOX. [in Russian]
4. Ershov A.G. Termicheskoe obezvrezhivanie othodov: teoriya i praktika, mify i legendy [Thermal waste disposal: theory and practice, myths and legends] / A.G. Ershov, V.L. Shubnikov // Tverdye bytovye othody [Solid household waste]. — 2014. — № 5 (95). — P. 46–52. — EDN SCPFUT. [in Russian]
5. Solomin I.A. Vybora optimal'noj tehnologii pererabotki TBO [Choosing optimal technology of solid household waste products recycling] / I.A. Solomin, V.N. Bashkin // Jekologija i promyshlennost' Rossii [Ecology and industry of Russia]. — 2005. — № 9. — P. 42–45. — EDN JXUKFH. [in Russian]
6. Fomenko A.I. Zola musoroszhigatel'nykh zavodov kak tehnogennyj syr'evoj resurs dlja izvlecheniya redkozemel'nykh jelementov [Ash from incinerators as a man-made raw material resource for the extraction of rare earth elements] / A.I. Fomenko, L.I. Sokolov // Jekologija i promyshlennost' Rossii [Ecology and industry of Russia]. — 2017. — Vol. 21. — № 12. — P. 28–31. — DOI: 10.18412/1816-0395-2017-12-28-31. — EDN ZUMFBB. [in Russian]
7. Buyantuev S.L. Waste Industrial Processing of Boron-Treated by Plasma Arc to Produce the Melt and Fiber Materials / S.L. Buyantuev, N. Guiling, E.T. Bazarsadaev [et al.] // Lecture Notes in Electrical Engineering. — 2016. — Vol. 365. — Chapter 38. — P. 353–361. — DOI: 10.1007/978-981-287-988-2\_38. — EDN WRWCHT.
8. Dvorkin L.I. Stroitel'nye materialy iz othodov promyshlennosti [Building materials from industrial waste] / L.I. Dvorkin, O.L. Dvorkin. — Moscow : Feniks, 2007. — 368 p. [in Russian]
9. Buyantuev S.L. K voprosu poluchenija kamennogo lit'ja iz bazal'ta mestnogo mestorozhdenija jelektrodugovym sposobom [On the issue of obtaining stone casting from basalt from a local deposit by electric arc method] / S.L. Buyantuev, A.S. Kondratenko, V.T. Buyantuev [et al.] // Vestnik Vostochno-Sibirskogo gosudarstvennogo universiteta tehnologii i upravlenija [Bulletin of the East Siberian State University of Technology and Management]. — 2023. — № 4 (91). — P. 87–95. — DOI: 10.53980/24131997\_2023\_4\_87. — EDN FPMLIS. [in Russian]
10. Weibel G. Chemical associations and mobilization of heavy metals in fly ash from municipal solid waste incineration / G. Weibel, U. Eggenberger, S. Schlumberger [et al.] // Waste Management. — 2017. — Vol. 62. — P. 147–159. — DOI: 10.1016/j.wasman.2016.12.004.

11. Buyantuev S.L. Recycling of the Ash Waste by Electric Plasma Treatment to Produce Fibrous Materials / S.L. Buyantuev, E.T. Bazarsadaev, A.B. Khmelev // *Lecture Notes in Electrical Engineering*. — 2016. — Vol. 365. — Chapter 34. — P. 319–326. — DOI: 10.1007/978-981-287-988-2\_34. — EDN WRWEPJ.
12. Nikiforov A.A. Issledovanie plazmennoj tehnologii poluchenija silikatnyh tugoplavkih rasplavov [Investigation of plasma technology for the production of silicate refractory melts] / A.A. Nikiforov, E.A. Maslov, N.K. Skripnikova [et al.] // *Teplofizika i aeromehanika* [Thermophysics and aeromechanics]. — 2009. — Vol. 16. — № 1. — P. 159–163. — EDN KJUKZF. [in Russian]
13. Gavrilenko V.V. Sovremennye metody issledovaniya mineralov, gornykh porod i rud [Modern methods of research of minerals, rocks and ores] / V.V. Gavrilenko. — Saint Petersburg : Saint Petersburg Mining University, 1997. — 137 p. [in Russian]
14. Paretskiy V.M. Poleznoe ispol'zovanie shlakov musoroszhiganiya [Useful use of waste incineration slags] / V.M. Paretskiy, A.A. Komkov, A.Yu. Mamaev // *Tverdye bytovye othody* [Solid household waste]. — 2011. — № 4 (58). — P. 51–56. — EDN NEAINB. [in Russian]
15. Sarkisov P.D. Izvlechenie stekla iz tverdykh gorodskih othodov [Extraction of glass from municipal solid waste] / P.D. Sarkisov, R.M. Chernyakova, P.D. Petrov // *Stekol'naja promyshlennost'* [Glass industry]. — 1986. — Issue 8. — P. 13–15. [in Russian]
16. Gonopolsky A.M. Nekotorye fiziko-himicheskie svoystva zoloshlakovykh othodov musoroszhigatel'nykh zavodov [Some physico-chemical properties of ash and slag waste from incinerators] / A.M. Gonopolsky, M.M. Dygan, A.A. Timofeeva // *Jekologija i promyshlennost' Rossii* [Ecology and industry of Russia]. — 2008. — № 7. — P. 36–39. — EDN JVRXBN. [in Russian]
17. Sitnikova V.E. Metody termicheskogo analiza. Praktikum [Methods of thermal analysis. Practicum] / V.E. Sitnikova, A.A. Ponomareva, M.V. Uspenskaya. — Saint Petersburg : ITMO University, 2021. — 152 p. — EDN SXYAMM. [in Russian]
18. Vlasov V.A. Plazmennye tehnologii sozdaniya i obrabotki stroitel'nykh materialov [Plasma technologies for the creation and processing of building materials] / V.A. Vlasov, G.G. Volokitin, N.K. Skripnikova [et al.]. — Tomsk : Scientific & Technical Literature Publishing House, 2018. — 512 p. [in Russian]
19. Buyantuev S.L. Pererabotka zoloshlakovykh othodov jelektrodugovoj plazmoj dlja poluchenija kompozicionnykh stroitel'nykh materialov [Processing of ash and slag waste by electric arc plasma for the production of composite building materials] / S.L. Buyantuev, L.A. Urkhanova, A.B. Khmelev [et al.] // *Vestnik VSGUTU* [Bulletin of the East Siberian State University of Technology and Management]. — 2016. — № 4 (61). — P. 19–26. — EDN WJSWUN. [in Russian]
20. Sarkisov P.D. Napravlenaja kristallizacija stekla – osnova poluchenija mnogofunkcional'nykh steklokristallicheskih materialov [Directed glass crystallization is the basis for obtaining multifunctional glass-crystalline materials] / P.D. Sarkisov. — Moscow : D. Mendeleev University of Chemical Technology of Russia, 1997. — 218 p. — EDN ZOPWAN. [in Russian]
21. Khudyakova L.I. Mestnoe syr'e dlja proizvodstva mineral'nogo volokna [Local raw materials for the production of mineral fiber] / L.I. Khudyakova, S.L. Buyantuev, V.T. Buyantuev // *Stroitel'nye materialy* [Building materials]. — 2022. — № 12. — P. 6–9. — DOI: 10.31659/0585-430X-2022-809-12-6-9. — EDN KXCFVP. [in Russian]
22. Shekhovtsov V.V. Poluchenie steklokeramiki sistemy MgO–SiO<sub>2</sub> metodom plazmennoj plavki [Production of glass ceramics of the MgO–SiO<sub>2</sub> system by plasma melting] / V.V. Shekhovtsov, O.G. Volokitin, V.A. Ushkov [et al.] // *Pis'ma v ZhTF* [Letters to the Journal of Technical Physics]. — 2022. — Vol. 48. — Issue 24. — P. 15–18. — DOI: 10.21883/PJTF.2022.24.54017.19278. — EDN WAAUDL. [in Russian]
23. Volokitin O.G. Osobennosti fiziko-himicheskikh processov poluchenija vysokotemperaturnykh silikatnykh rasplavov [Features of physico-chemical processes for obtaining high-temperature silicate melts] / O.G. Volokitin, V.I. Vereshchagin // *Izvestija vuzov. Himija i himicheskaja tehnologija* [Universities News. Chemistry and Chemical Technology]. — 2013. — Vol. 56. — № 8. — P. 71–76. — EDN QZESVF. [in Russian]
24. Pavlushkin N.M. Himicheskaja tehnologija stekla i sitalov [Chemical technology of glass and metals] / N.M. Pavlushkin. — Moscow : Strojizdat, 1983. — 432 p. [in Russian]
25. Khan B.H. Ocenka tehnologicheskikh harakteristik petrurgicheskikh rasplavov pri ispol'zovanii piroksenovogo modulja [Evaluation of the technological characteristics of petrurgic melts using a pyroxene module] / B.H. Khan, M.B. Stroshchenko // *Problemy kamennogo lit'ja* [Problems of stone casting]. — Kiev : Naukova Dumka, 1975. — Issue 3. — P. 184–192. [in Russian]
26. Lyasin V.F. Oblicevochnye stekljannye i steklokristallicheskie materialy [Facing glass and glass-crystalline materials] / V.F. Lyasin, P.D. Sarkisov. — Moscow : Higher School, 1988. — 146 p. — EDN ZOPEYH. [in Russian]